

Innovative and Eco-Friendly Concrete Forming Sustainable and Resilient Structures Using Waste Marble Powder

Mohammad Ajmal Khan

M. Tech Scholar, Department of Civil Engineering, Punjabi University, Patiala, India

Correspondence should be addressed to Mohammad Ajmal Khan; mohammadajmalkhanpbuni@gmail.com

Received: 5 June 2024

Revised: 17 June 2024

Accepted: 30 June 2024

Copyright © 2024 Made Mohammed Ajmal Khan. This is an open-access article distributed under the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

ABSTRACT: In recent years, India has witnessed a remarkable and swift growth in the use of concrete and with this the carbon footprints have skyrocketed resulting in global warming. The carbon footprints generated by concrete manufacturing can be minimized by incorporating waste materials and one such material which can be utilized is waste marble powder (WMP). The marble manufacturing industry generates an enormous quantity of waste during sawing and cutting, leading to an adverse influence on the environment. This possesses an environmental requirement to recycle this waste. Our study deduced that concrete can be made more sustainable and durable, achieving reduction in carbon content, if waste marble powder is substituted for fine aggregates. From an environmental perspective, this development is beneficial since it will marginalize sand extraction from the river beds at a large-scale as this factor leads to detrimental effects on our ecosystem. We aimed to incorporate WMP into concrete at distinct proportions and partially replace fine aggregate with WMP. In the experiments, both destructive and non-destructive techniques were used. The water-to-cement ratio was maintained at 0.45 while four different concrete mixtures were tested at weight ratios of 10%, 20%, 30%, and 40%. When fine aggregate is substituted with WMP at a weight ratio of 40%, the best outcome is achieved, enhancing concrete's inherent properties. The compressive strength, split tensile strength and flexural strength test results have all improved by 35%, 17.5%, and 27%, respectively after curing period of 365 days. Rebound hammer test obtained maximum value of 42.72 N/mm², an increment of 15%; ultrasonic pulse velocity (UPV) demonstrated a gain of 3% at 40% replacement ratio; rate of water absorption decreases by 46% for cubes, 40% for cylinders and 36% for beams.

KEYWORDS: Sustainable concrete, Waste marble powder, Carbon capture, Eco-concrete, Compressive strength, Flexural strength, Tensile strength, Rebound hammer, Ultrasonic pulse velocity, Water absorption

I. INTRODUCTION

Concrete has emerged as the most widely employed substance for construction throughout the globe [1] because of its durability and serviceability [2]. Planet's natural resources are declining on account of the construction industry's ever-growing requirement for concrete manufacturing, which is composed of cement, fine aggregates, coarse aggregates, and water [3]. Continuous

consumption of aggregates is gradually depleting natural resources (fine and coarse aggregates) much more steadily than they are replenished [2] and it is anticipated that the cement production will hit 4.1 billion tons in 2022, compared to 1.39 billion tons in 1995, indicating how rapidly building construction industry has developed since then [4]. Considering the enormous utilization of concrete and skyrocketing consumption of sand and aggregates, manufacturing eco-friendly concrete is indispensable and researchers are actively looking for better alternatives that can improve qualities of concrete with the goal to cater to the rise in demand for construction [5]. In an effort to use fewer natural resources, researchers are investigating the use of waste materials in concrete as substitutes of coarse aggregates and natural sand. During manufacturing of marble in industries, waste marble powder (see Figure 1) is produced and owing to environmental concerns, as it increases pollution, its disposal has emerged as one of the most contentious issues [6][7]. During the stages of mining, processing, and polishing, about 70% (see Figure 2) of marble is wasted [8]. Since the beginning of time, it has been utilized for flooring and decorative reasons. An estimated 7 million tons of waste marble is produced annually from 30 to 60% of the stones that are excavated and processed [9]. India is the world's third-largest producer of marble powder, accounting for about 10% of the global supply [10]. Land contamination is a result of disposing of waste marble powder in landfills. Reduced soil fertility and poor soil characteristics could also result from a possible marble powder disposal issue [7]. Since marble powder and concrete have a negative impact on the environment [1], developing a solution is crucial to cut pollution. WMP can be used to fully or partially replace sand in concrete, conserving natural resources while trimming the carbon emissions stemming from the manufacturing of cement [2]. Investigation carried out by [11] revealed that by partially replacing sand with WMP (in concrete) results are improved due to its fineness quality and environmentally sustainable nature [12] of waste marble powder. Adding waste marble powder to concrete as a partial replacement enhances its workability [13] and concrete's strength qualities can be enhanced by WMP up to a certain point [14].

Waste marble powder is an important and practical choice to be used as a construction material in the building industry since it raises the characteristics of concrete while minimizing the consumption quantity of cement and natural (fine and coarse) aggregates. The fundamental objective of

this research endeavor is to manufacture innovative, sustainable and eco-friendly concrete by partially replacing sand with waste marble powder at different percentages by weight of sand in concrete.



Figure 1: Waste Marble Powder (WMP)

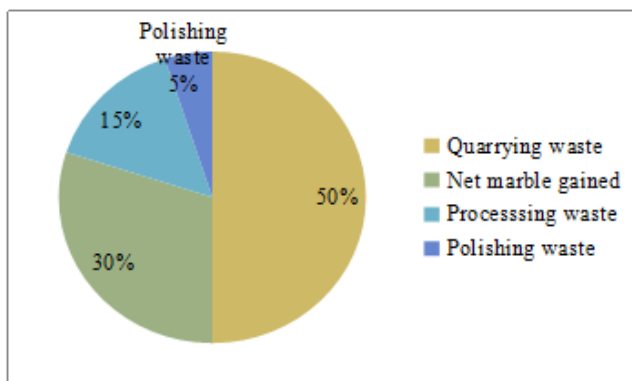


Figure 2: Marble product and waste (% age mined out)^[8]

II. OBJECTIVES

The objectives of the research work are as follows:

- i) Investigation of strength performance of concrete after 28 days of curing by replacing fine aggregates with Waste Marble Powder at replacement levels of 0%, 10%, 20%, 30% and 40% by destructive testing of concrete.
 - Compressive Strength
 - Split Tensile Strength
 - Flexural Strength
- ii) Non-destructive testing of concrete after 28 days of curing at replacement levels of 0%, 10%, 20%, 30% and 40%.
 - Rebound Hammer
 - Ultrasonic Pulse Velocity
- iii) Durability Test of concrete mixtures at replacement levels of 0%, 10%, 20%, 30% and 40% for cubes, cylinders and beams.
 - Water Absorption

The results of the study will provide the construction industry with valuable insights on how to reduce waste production, improve the performance of concrete, and deploy environmentally friendly procedures.

III. LITERATURE REVIEW

The studies of Olutoge et al. states that by incorporating waste marble powder to replace up to 10% by weight of fine sand in concrete, it is possible to enhance both its tensile and compressive strength. The utilization of marble powder in the production of concrete presents environmental benefits as well. Waste management opportunities are thus showcased, offering potential application in low-traffic roads, stone pitching, earthworks, flexible pavement foundations, and smaller-scale concrete works. Following research by Olutoge, Onugba, and Ocholi, it was found that concrete's compressive strength improves with the addition of marble powder, provided it is used within an appropriate limit of 15%. Consequently, they concluded that marble powder can indeed serve as a substitute for sand in concrete. Mixtures that contain a concentration of marble powder, specifically less than 15% of Waste Marble Powder (WMP) content, have been found to enhance the mechanical properties of concrete. Additionally, the use of WMP contributes to the conservation of natural sand resources by providing a sustainable method for disposing of waste materials from the construction industry. The mechanical and physical attributes of concrete can be further improved by maintaining a low water-cement ratio [15]. The conclusions drawn from the research conducted by Hebhouh et al. illustrate that the concrete samples, created with the inclusion of marble powder, demonstrated mechanical properties that adhered to the production specifications for concrete. It was found that up to 75% of any given formulation could be composed of marble aggregates as a substitute for natural aggregates, thereby enhancing the concrete's tolerance [16]. Research studies of Cornialdesi et al. found that the substitution of marble powder for sand at a rate of 10% resulted in an enhancement of compressive strength, while maintaining the same level of workability [17]. The investigation led by Demirel Bahar and fellow researchers discovered that, replacement of Waste Marble Powder (WMP) with cement or sand enhances both the fresh and hardened properties of traditional and Self-Compacting Concrete (SCC) and implementation of WMP as a substitute for raw materials sourced from natural resources, like sand and coarse aggregate, results in lower energy consumption and reduced usage of these resources [12]. The exploration carried out by Idress et al. replaced sand with marble powder in amounts of 12.5%, 25% and 50% to produce concrete mixtures and studied impact of marble powder replacements on various factors such as tensile, compressive and flexural strengths, workability and cost were examined and found that the workability was adversely affected by the introduction of marble powder. However, a replacement level of 12.5% resulted in increased strength, while further substitution led to a decrease in strength, albeit to an acceptable degree. When used in appropriate quantities, marble powder either improved mechanical properties or yielded satisfactory strength results (even at higher percentages). The use of marble powder as a substitute for natural sand can contribute to resolving environmental, economic, and ecological issues linked with concrete production, thereby promoting sustainability [18]. Key findings from the study of Basaran et al. research investigations demonstrated that replacing fine aggregates in concrete with marble powder, up to a proportion of 15%, positively influences the compressive strength of the

concrete. This advantageous effect ranged from 2% to 26% establishing that marble powder can potentially enhance the compressive strength of concrete by as much as 45% [19]. Ghani et. al. observed notable reductions of 26%, 65%, 93%, and 100% at replacement rates of 20%, 40%, 60%, and 80% respectively. The incorporation of increasing proportions of marble powder led to a decrease in the overall weight of the concrete, owing to the relatively low density of Waste Marble Powder (WMP). This also resulted in an increase in compressive strength up to a 40% substitution of fine aggregate; however, the strength progressively diminishes if the percentage is further increased. A reduction in the permeability of concrete was noted with a higher content of WMP, but a significant surge in permeability was detected at a replacement level of 80%. These researchers advocated for the use of marble powder up to 40% by weight of sand as an alternative material, as excessive usage can weaken the concrete and make it more difficult to manage [14]. Research conducted by Vardhan et al. has indicated that substituting up to 40% of sand with marble waste aggregates results in the optimal increase in compressive strength and reduction in drying shrinkage of concrete mixes. The compressive strength experienced a rise of 20%, while drying shrinkage was reduced by 30%. Experiments were conducted on six different mixtures, each incorporating marble powder at varying percentages ranging from 10 to 60%. These tests evaluated the permeation properties, tensile strength, and compressive strength of the concrete after a period of 365 days (about 12 months). X-Ray Diffraction (XRD) and Scanning Electron Microscopy (SEM) investigations were also undertaken. Based on the test outcomes, the addition of Waste Marble Powder (WMP) to concrete was found to enhance its strength and permeability characteristics. A substitution rate of 40% offered the most significant advantages. The findings confirmed that WMP can effectively replace fine aggregate in concrete, thereby augmenting overall performance and promoting consistent progress [20]. Singh & Mehta carried out experiments on mixtures incorporating marble powder as a substitute for 10%, 20%, 30%, 40%, and 50% of the fine aggregate. The durability of the geo-polymer concrete was assessed after the first and fourth weeks (7 & 28 days). The findings indicate that the compressive strength is enhanced when Waste Marble Powder (WMP) is used to replace 60% of the fine aggregate. Additionally, both flexural and split tensile strengths experience significant increases, amplifying by 60% and 80% respectively upon replacement [21]. Vigneshpandian et al. research scrutinized the effects of substituting 25%, 50%, and 100% of Waste Marble Powder (WMP) on the flexural, tensile, and compressive strengths of concrete. The findings suggested that the properties of concrete could be enhanced up to a replacement level of 50%, without compromising its performance [22]. Li et al. conducted a series of tests, including water absorption, drying shrinkage, mini slump cone, and carbonation, were conducted on a range of mortar mixes formulated with varying mix design volumes and water-cement ratios and the incorporation of marble dust notably amplified the carbonation and water resistances, diminished the shrinkage strain and rate, and curtailed the cement content by as much as 33% [23]. The studies of Alyamac & Aydin [13] depicted that by replacing up to 40% of sand (by weight) with waste marble powder, yields satisfactory outcomes for compressive strength, slump

value, sorptivity and abrasion resistance of concrete. The literature review of the research conducted by Sarkar et al. says that the process of cutting and sawing of marble generates a fine marble dust, which, if relegated to a landfill, can precipitate a myriad of health complications and diminish soil fertility [7]. Research of [6] has indicated that marble industries frequently discard their waste in verdant and open spaces. This practice could potentially instigate water stagnation problems and escalate soil alkalinity. Consequently, this may precipitate issues related to soil fertility and contribute to terrestrial and aquatic pollution. The findings of Maan and Ahed demonstrated that the fine-grained nature of marble powder contributes to fostering cohesiveness among particles, even when maintaining a low water-cement ratio and the incorporation of a specific quantity of marble powder in concrete can aid in augmenting its strength and enhancing its microstructural properties [11]. Investigation led by Ali M. Abdullah et al. indicated that the presence of calcium carbonate, a constituent of marble powder, facilitates more efficient particle packing when waste marble powder is incorporated into the mixture [24]. Kanoungo and his fellow researchers designed a mix using fly ash and lime sludge as substitutes for cement, the compressive strength of the prepared mix was determined through an unconfined compressive strength test. The optimal proportions of cement, fly ash, and sludge were found to be 20%, 40%, and 40% respectively, significantly reducing the cement content. It was subsequently established that, contingent on the curing technique utilized, the strength of the ideal mix increased by 31% in every case when fly ash and sludge were proportionally substituted for cement confirming the effect of waste materials on the properties of concrete [8]. Topcu et al. found that a marble dust content of 200 Kg/m³ could enhance the capillarity coefficient when marble dust was employed as a partial substitute for the cement and fly ash binder in Self-Compacting Concrete (SCC) [25].

IV. EXPERIMENTAL SETUP

Components integrated into the concrete, along with the calculations of fineness modulus, specific gravity, and moisture content, are being evaluated and given in Table 1.

- Cement
- Sand
- Coarse Aggregates
- Waste Marble Powder
- Water
- Super plasticizer

A. Materials Employed

- **Cement:** With reference to the specifications outlined in Bureau of Indian Standard code IS: 269-1976, research was conducted on Ordinary Portland Cement (OPC) 43. Slump test was conducted in compliance with Indian Standard code IS: 1199-1959 and the slump value was determined to be 78mm after ten minutes.
- **Coarse Aggregate:** Dolomite, nominally sized at a range of 10mm (minimum) to 20mm (maximum) conforming to the specifications corresponding to the Bureau of Indian Standard code IS: 383-2016.
- **Fine Aggregate:** Sand employed was having a fineness modulus of 2.83 conforming to the

specifications as stated by Bureau of Indian Standard code IS: 383-2016 and ASTM C128.

- **Superplasticizer:** Shalplast PCE 200 was added to assist in making cement more workable.
- **Water:** Potable
- **Marble powder:** Powdered marble was obtained from the marble industry.

Table 1: Calculated Fineness modulus, specific gravity, moisture content of cement, coarse aggregate, fine aggregate and waste marble powder

S.No.	Materials Employed	Fineness Modulus	Specific Gravity	Moisture Content
1.	Cement	Less than 2%	3.39	0.7%
2.	Coarse Aggregate	6.25	2.538	2.27%
3.	Fine Aggregate (sand)	2.83	2.08	2.14%
4.	Waste Marble Powder	3.29	2.46	1.01%

Physical characteristics of waste marble powder are given in Table 2 and chemical composition is given in Table 3

Table 2: Physical characteristics of Waste Marble Powder [8]

Color	White
Moisture content	1.01%
Odor	Odorless
Form	Powder
Density	2.80
Specific gravity	2.46

Table 3: Chemical components of Waste Marble Powder [8]

Oxide compounds	Marble powder (Mass %)
SiO ₂	28.35
Al ₂ O ₃	0.42
Fe ₂ O ₃	9.70
Cano	40.45
MgO	16.25

B. Concrete Mixtures

For 1m³ of M30 Grade concrete the quantity of materials required is 332 Kg of cement, 560 Kg of Fine Aggregates, 1213 Kg of Coarse Aggregates, 1.08 Kg of Superplasticizer and 149 liters of water.

Five M30 grade concrete mixtures were formulated in accordance with IS: 1199-1959 and IS: 10262-2019 employing diverse quantities of Waste Marble Powder (WMP). The corresponding mix design calculation is presented in Table 4 below. A consistent water/cement ratio of 0.45 was preserved throughout the laboratory work. Shalplast PCE 200 was incorporated at a rate of 0.3% of the total weight of cementitious materials. WMP was substituted for sand in the following proportions: 0%, 10%, 20%, 30%, and 40%. Table 5, Table 6 and Table 7 display the concrete mixture proportions for cubes, cylinders and beams casting respectively.

Table 4: Mix Design Calculations

Required Quantity	Cement (Kg)	Fine Aggregates (Kg)	Coarse aggregates (Kg)	Water-cement ratio	Super Plasticizer (L)
For 1m ³ of concrete	332	560	1213	0.45	0.996
Mix ratio	1	1.68	3.65		

Table 5: Quantity of material required for cube casting (150 mm x 150 mm x 150 mm)

S.No.	Percentage (%)	Fine aggregates (Kg)		Cement (Kg)	Coarse Aggregates (Kg)	Water (L)	Super plasticizer (ml)
		Sand	WMP				
1.	0%	2.5	0	1.39	4.58	0.62	4.13
2.	10%	2.0	0.25				
3.	20%	2.1	0.50				
4.	30%	1.8	0.75				
5.	40%	1.4	1.00				

Table 6: Quantity of material required for cylinder casting (150 mm x 300 mm)

S.No.	Percentage (%)	Fine aggregates (Kg)		Cement (Kg)	Coarse Aggregates (Kg)	Water (L)	Super plasticizer (ml)
		Sand	WMP				
1.	0%	3.95	0	2.18	7.87	0.98	6.51
2.	10%	3.55	0.395				
3.	20%	3.16	0.79				
4.	30%	2.76	1.185				
5.	40%	2.37	1.58				

Table 7: Quantity of material required for beam casting (100 mm x 100 mm x 500 mm)

S.No.	Percentage (%)	Fine aggregates (Kg)		Cement (Kg)	Coarse aggregates (Kg)	Water (L)	Super plasticizer (ml)
		Sand	WMP				
1.	0%	3.7	0				
2.	10%	3.3	0.3				

	%	5	7				
3.	20	2.9	0.7	2.07	6.78	0.93	6.23
	%	8	4				
4.	30	2.6	1.1				
	%	1	1				
5.	40	2.2	1.4				
	%	3	9				

V. TESTING

Concrete grade M30 was produced by replacing sand with WMP at ratios of 0%, 10%, 20%, 30%, and 40% by sand weight. A constant 0.3% superplasticizer was added to cement by weight to increase the workability of concrete. To represent each percentage (0%, 10%, 20%, 30%, and 40%), 30 cubes, 30 cylinders, and 30 beams were cast.

On the 28th day of curing, destructive and non-destructive testing of concrete samples was done for assessing compressive strength, splitting tensile strength, flexural strength, rebound hammer, ultrasonic pulse velocity (UPV), and water absorption.

With the application of non-destructive testing, the durability qualities of freshly made concrete were evaluated, while destructive testing assisted in analyzing the mechanical properties of the material of concrete.

A. Destructive Testing

• Compressive Strength Test

Following a 28-day curing period, samples were tested for compressive strength in conformity with specifications of IS-456:2000. Cube specimens of 150 mm x 150 mm x 150 mm were used to study the compressive strength. Curing was applied to every sample. Six samples were examined, and the mean value was determined. Testing was conducted using the compression testing machine. The compression machine had a capacity of 2000 kilo-Newtons (kN).

• Split Tensile Strength

In congruence with the Indian Standards code of practice IS-5816:1999 specifications, cylindrical specimens' (150 mm x 300 mm) tensile strength was assessed after 28 days. Six cylinders were tested, and the outcome was determined by taking the average of six values.

• Flexural Strength Test

Beams measuring 100 mm x 100 mm x 500 mm were evaluated on a flexural strength testing equipment after 28 days of curing. Flexural strength was assessed and evaluated in compliance with Indian standard code IS-516:1999. The outcome was determined by averaging the values of six samples.

B. Non - destructive Testing

• Rebound hammer test

Cubes of 150 x 150 mm x 150 mm x 150 mm were subjected to a rebound hammer test or Schimdt hammer test after 28 days of curing, in accordance with IS-13311Part 2:1992. Nine results were obtained for each cube after testing six cube samples. The average value of all nine values was computed to arrive at the result.

• Ultrasonic Pulse Velocity test (UPV)

With the use of a UPV tester, the 150mm x 150mm x 150mm cubes were subjected to an ultrasonic pulse velocity

test after twenty-eight days of cure. Before being affixed on the cubes' faces, the transmitter and receiver were covered in gel. The tester tracked velocity in meters per second (m/s) for all cube percentages. The technique used was direct transmission with opposing faces in accordance with the Indian Standards Code of Practice IS-13311:1992.

C. Durability Test

• Water Absorption Test

Weights of cube, cylinder and beam specimens were ascertained under dry conditions as well as following a 24-hour immersion in water. The weights were utilized to calculate any increases or decreases in the specimen's overall weight.

Water absorption (%) = $[(B-A)/A] \times 100$ where, A = dry weight.

B = weight after being submerged in water for 24 hours.

The water absorption test was conducted in compliance with IS-1124:1974, method of test for determination of water absorption of concrete.

All the tests were carried under controlled environment and apart from above listed Indian Standard Codes, code IS-516:1959, ASTM C293 and ASTM C128 were religiously followed for the execution of tests.

VI. RESULTS AND DISCUSSION

A. Results of Destructive Tests

• Compressive Strength Test

Table 8 give an overview of the measured compressive strengths of the concrete for various WMP ratios. The proportion of marble powder replacement causes a spike in compressive strength. The results indicate that the combination with the highest compressive strength was 40%. At the 28-day curing period, the compressive strengths were 30.17 MPa, 31.32 MPa, 32.14 MPa, 34.32 MPa, and 35.45 MPa for 0%, 10%, 20%, 30%, and 40%, respectively.

Table 8: Results of compressive strength test after 28 days

Serial No.	Cubes (150×150×150) (mm)	Peak Load (kN)	Compressive strength (MPa)
1.	0%	676.5	30.17
2.	10%	678.9	31.32
3.	20%	681.3	32.14
4.	30%	772.3	34.32
5.	40%	797.8	35.45

• Splitting Tensile Strength

As demonstrated by Table 9, strength increases to its maximum peak value of 2.48 N/mm² after 28 days of curing when 40% of the sand is replaced with WMP.

Table 9: Results of Split Tensile Strength after 28 days

Serial No	Cylinder (300mm×150mm)	Peak load, P (kN)	Compressive strength (MPa)	Tensile strength (in N/mm ²)
1.	0%	138.2	7.82	1.95
2.	10%	144.7	8.18	2.05
3.	20%	148.9	8.28	2.09
4.	30%	164.5	9.30	2.32

5.	40%	175.3	9.92	2.48
----	-----	-------	------	------

- **Flexural Strength**

Final outcomes of flexural strength test are shown in Table 10. The highest flexural strength was found in an amalgamation that included 40% WMP, an increment of 35%. Following a 28-day curing period, the values for 0%, 10%, 20%, 30%, and 40% were 0.68 N/mm², 0.74 N/mm², 0.78 N/mm², 0.85 N/mm², and 0.92 N/mm² respectively.

Table 10: Results of Flexural Strength Test after 28 days

Serial No.	Beam (500mm×100×100)	Peak load (P) (kN)	Flexural strength (MPa)	Distance between the line of failure and nearest support 'a'
1.	0%	1.70	0.68	160 mm
2.	10%	1.87	0.74	130 mm
3.	20%	2.30	0.78	170 mm
4.	30%	2.55	0.85	155 mm
5.	40%	2.85	0.92	195 mm

B. Results of Non-destructive Tests

- **Rebound Hammer**

Mixture yielded the highest values for the rebound hammer test was achieved at 40% substitution of sand with WMP. Table 11 below illustrate the test's results.

Table 11: Values of Rebound Hammer Test

Serial No.	Cube	Mean value (N/mm ²)
1.	0%	37.37
2.	10%	40.81
3.	20%	41.37
4.	30%	42.46
5.	40%	42.72

- **Ultrasonic Pulse Velocity Test (UPV)**

Table 12 convey a schematic representation of the UPV test of the concrete after 28 days of the cure process. As the WMP proportion rises, velocity rises as well. Due to the waste marble powder's filler effect, the greatest velocity is attained when sand is replaced with it by 40%.

Table 12: Values of UPV test after 28 days

Serial No.	Cube	Velocity (Km/hr)
1.	0%	4573
2.	10%	4607
3.	20%	4658
4.	30%	4693
5.	40%	4713

C. Results of Durability Test

- **Water Absorption Test**

As proportion of WMP in concrete mixture rises, it can be deduced from Table 13, Table 14 and Table 15 that the

structure becomes less porous, resulting in a decrease in water absorption. As a result, water cannot damage the structure or flow within.

- **Cubes**

Table 13: Water absorption test results of cubes

Serial No.	Percent ages (%)	Saturated dry weight (Kg)	Saturated wet weight (Kg)	Water absorption (%) {Formula: dry wt. – wet wt. / dry wt.} × 100
1.	0%	8.12 Kg	8.13 Kg	0.35
2.	10%	8.22 Kg	8.28 Kg	0.33
3.	20%	8.22 Kg	8.27 Kg	0.29
4.	30%	8.27 Kg	8.31 Kg	0.23
5.	40%	8.36 Kg	8.38 Kg	0.19

- **Cylinders**

Table 14: Water absorption test results of cylinders

Serial No.	Percent ages (%)	Saturated dry weight (Kg)	Saturated wet weight (Kg)	Water absorption (%) {Formula: dry wt. – wet wt. / dry wt.} × 100
1.	0%	12.79 Kg	12.87 Kg	0.68
2.	10%	12.29 Kg	12.38 Kg	0.61
3.	20%	12.54 Kg	12.65 Kg	0.53
4.	30%	12.77 Kg	12.83 Kg	0.48
5.	40%	12.94 Kg	13.01 Kg	0.41

- **Beams**

Table 15: Water Absorption Test Result of Beams

Serial No.	Percent ages (%)	Saturated dry weight (Kg)	Saturated wet weight (Kg)	Water absorption (%) {Formula: dry wt. – wet wt. / dry wt.} × 100
1.	0%	12.15 Kg	12.27 Kg	0.98
2.	10%	12.40 Kg	12.50 Kg	0.97
3.	20%	12.35 Kg	12.47 Kg	0.81
4.	30%	12.49 Kg	12.63 Kg	0.79
5.	40%	12.68 Kg	12.76 Kg	0.63

VII. CONCLUSION

Considering above study's findings following developments are established:

- By incorporating Waste Marble Powder concrete's compressive strength boosted by 17.5% at 40% replacement of fine aggregates and reached value of 35.45 MPa. Due to marble powder's enhanced fineness, it was able to occupy more pores, which boosted compressive strength. Owing to this reason, WMP particles absorb water more quickly; the amount of water in the cement mixture is reduced, increasing the compressive strength.
- Employing Waste Marble Powder in designing concrete improved the Split tensile strength of concrete. At substitution level of 40%, highest value turns out to be 2.48 N/mm², experiencing a 27% rise.
- Flexural strength of concrete boosted by 35%. The maximum strength recorded is 0.92 MPa at 40% replacement of fine aggregates with Waste Marble Powder.
- Improved results of Rebound Hammer testified to improvement of compressive strength. Concrete mix at 10% replacement level gained value of 37.37 N/mm² and witnessed a significant rise at replacement level of 40% of fine aggregates with Waste Marble powder, reaching highest value of 42.72 N/mm², an increment of 15%.
- Sound results of Ultrasonic Pulse Velocity test signified better quality and structural integrity of concrete as the velocity increased from 4573 Kilometer per hour (km/hr) to 4713 Kilometer per hour (km/hr) at 0% and 40% replacement level respectively, showing a gain of 3%.
- At 40% replacement, water absorption rate falls by 46% for cubes, 40% for cylinders and 36% for beams. Decline in Water Absorption level in concrete testifies to its enhanced durability. This corresponds to the filler action of Waste Marble Powder thus; it can be concluded using raising marble powder content significantly reduces the porous nature of the concrete.

VIII. FUTURE SCOPE AND LIMITATIONS

- Considering the high fineness of waste marble powder, it was helpful in maintaining high cohesion with the constituent parts of concrete when combined with a super-plasticizing admixture. If widely used as building material, it could also serve as a potential solution for resolving concerns about landfill disposal.
- Using waste marble powder in the building industry may be a cost-effective option on account of free availability and an easily procurable resource.
- Incorporation of waste marble powder in concrete cuts the quantity of cement used and will help in producing eco-concrete.
- Waste marble incorporation could only be practicable through comprehensive research and an understanding of this area of expertise.
- In order to facilitate the use of WMP as an accessible alternative to fine aggregates in concrete, this endeavor requires support from the government at all levels. Standard guidelines and guidance are needed to help engineers and professionals in the construction and environmental sectors recognize this use of WMP.

ACKNOWLEDGMENT

I am highly grateful to the Department of Civil engineering, Punjabi University Patiala for guiding me to carry out my research project on "Innovative and eco-friendly concrete forming sustainable and resilient structures using Waste Marble Powder". Great appreciation goes to the faculty of civil engineering for giving me the chance to work in practical setting to further enhance my practical skills. This project is accomplished with the guidance of all. Working on this project has proved highly beneficial to me and I have gained abundant knowledge regarding the application of marble dust in concrete.

CONFLICTS OF INTEREST

The authors declare that they have no conflicts of interest between them and with any third party.

REFERENCES

- [1] SOHU, S., JHATIAL, A. A., ULLAH, K., LAKHIAR, M. T., & SHAHZAIB, J. Determining the Critical Success Factors for Highway Construction Projects in Pakistan. *Engineering, Technology & Applied Science Research*, Vol No. 8(2), 2018 p.p. 2685–2688. Available from: <https://doi.org/10.48084/etasr.1866>
- [2] MEMON, M. J., JHATIAL, A. A., RID, Z. A., RIND, T. A., & SANDHU, A. R. Marble Powder as Fine Aggregates in Concrete. *Engineering, Technology & Applied Science Research*, Vol. No. 9(3), 2019 p.p. 4105–4107. Available from: <https://doi.org/10.48084/etasr.2698>
- [3] BOURZIK, O., BABA, K., AKKOURI, N., & NOUNAH, A. Effect of waste marble powder on the properties of concrete. *Materials Today: Proceedings*, 72, 2023 p.p. 3265–3269. Available from: <https://doi.org/10.1016/j.matpr.2022.07.184>
- [4] Global cement production 1995-2022, M. Garside, Statista.com, October, 2023 <https://www.statista.com/statistics/1087115/global-cement-production-volume/>
- [5] RANA, A., KALLA, P., VERMA, H. K., & MOHNOT, J. K. Recycling of dimensional stone waste in concrete: A review. *Journal of Cleaner Production* Vol. No. 135, 2016 p.p. 312–331. Available from: <https://doi.org/10.1016/j.jclepro.2016.06.126>
- [6] SINHA, R., KUMAR, S., GARG, S., PRASAD, N. M. Use of electronic waste plastic in asphalt mix with marble dust as filler. *Indian Journal of Engineering and Materials Sciences*, Vol. No. 28(01), 2021. Available from: <https://doi.org/10.56042/ijems.v28i1.31357>
- [7] SARKAR, R., DAS, S.K., MANDAL, P.K., & MAITI, H.S. Phase and microstructure evolution during hydrothermal solidification of clay-quartz mixture with marble dust source of reactive lime. *Journal of the European Ceramic Society*, Vol. No 26(3), 2006 p.p. 297–304. Available from: <https://doi.org/10.1016/j.jeurceramsoc.2004.11.006>
- [8] KANOUNGO, S. K., SHARMA, U., & KANOUNGO, A. Utilization of Waste Lime Sludge and Coal Fly Ash in Construction Industry. *Sustainable Environment and Infrastructure*, 2020 p.p.281–292. Available from: https://doi.org/10.1007/978-3-030-51354-2_25
- [9] KRISHNAN, S., EMMANUEL, A. C., KANAUIA, S. K., & BISHNOI, S. Hydration and Mechanical Properties of Limestone Calcined Clay Cement Produced with Marble Dust. *Calcined Clays for Sustainable Concrete*, 2017 p.p. 249–253. Available from: https://doi.org/10.1007/978-94-024-1207-9_40
- [10] ASHISH, D. K. Concrete made with waste marble powder and supplementary cementitious material for sustainable

- development. *Journal of Cleaner Production*, Vol. No. 211, 2019 p.p. 716–729. Available from: <https://doi.org/10.1016/j.jclepro.2018.11.245>
- [11] HABIB, A., & HABIB, M. Sustainable Recycling of Marble Dust as Cement Replacement in Concrete: Advances and Recent Trends. *Cement Industry - Optimization, Characterization and Sustainable Application*, 2021. Available from: <https://doi.org/10.5772/intechopen.93915>
- [12] DEMIREL, B., & ALYAMAC, K. E. Waste marble powder/dust. *Waste and Supplementary Cementitious Materials in Concrete*, 2018 p.p. 181–197. Available from: <https://doi.org/10.1016/b978-0-08-102156-9.00006-7>
- [13] ALYAMAC, K. E., & AYDIN, A. B. Concrete properties containing fine aggregate marble powder. *KSCE Journal of Civil Engineering*, Vol No. 19(7), 2015 p.p. 2208–2216. Available from: <https://doi.org/10.1007/s12205-015-0327-y>
- [14] GHANI, A., ALI, Z., KHAN, F. A., SHAH, S. R., KHAN, S. W., & RASHID, M. Experimental study on the behavior of waste marble powder as partial replacement of sand in concrete. *SN Applied Sciences*, Vol. No. 2(9), 2020. Available from: <https://doi.org/10.1007/s42452-020-03349-y>
- [15] OLUTOGE, F., ONUGBA, M., & OCHOLI, A. Strength Properties of Concrete Produced with Iron Filings as Sand Replacement. *British Journal of Applied Science & Technology*, Vol. No. 18(3), 2016 p.p. 1–6. Available from: <https://doi.org/10.9734/bjast/2016/29938>
- [16] HEBHOUB, H., AOUN, H., BELACHIA, M., HOUARI, H., & GHORBEL, E. Use of waste marble aggregates in concrete. *Construction and Building Materials*, Vol No. 25(3), 2011 p.p. 1167–1171. Available from: <https://doi.org/10.1016/j.conbuildmat.2010.09.037>
- [17] CORINALDESI, V., MORICONI, G., & NAIK, T. R. Characterization of marble powder for its use in mortar and concrete. *Construction and Building Materials*, Vol No. 24(1), 2010 p.p. 113–117. Available from: <https://doi.org/10.1016/j.conbuildmat.2009.08.013>
- [18] IDREES, M., & FAIZ, A. Utilization of waste quarry dust and marble powder in concrete, *Sustainable Construction Materials and Technologies (SCMT)*, 2019. Available from: <https://doi.org/10.18552/2019/idsomt5035>
- [19] BASARAN, B., KALKAN, I., AKSOYLU, C., ÖZKILIC, Y. O., & SABRI, M. M. S. Effects of Waste Powder, Fine and Coarse Marble Aggregates on Concrete Compressive Strength. *Sustainability*, Vol. No. 14(21), 2022. Available from: <https://doi.org/10.3390/su142114388>
- [20] VARDHAN, K., SIDDIQUE, R., & GOYAL, S. Influence of marble waste as partial replacement of fine aggregates on strength and drying shrinkage of concrete, *Construction and Building Materials*, Vol. No. 228, 2019. Available from: <https://doi.org/10.1016/j.conbuildmat.2019.116730>; & VARDHAN, K., SIDDIQUE, R., & GOYAL, S. Strength, permeation and micro-structural characteristics of concrete incorporating waste marble, *Construction and Building Materials*, Vol. No. 203, 2019 p.p. 45–55. Available from: <https://doi.org/10.1016/j.conbuildmat.2019.01.079>
- [21] SINGH, A., & MEHTA, S. Partial replacement of fine aggregate with copper slag and marble dust powder in geopolymer concrete: A review. *IOP Conference Series: Earth and Environmental Science*, Vol. No. 889(1), 2021. Available from: <https://doi.org/10.1088/1755-1315/889/1/012070>
- [22] VIGNESHPANDIAN, G. V., SHRUTHI, E. A., VENKATASUBRAMANIAN, C., & MUTHU, D. Utilisation of Waste Marble Dust as Fine Aggregate in Concrete. *IOP Conference Series: Earth and Environmental Science*, Vol. No. 80, 2017. Available from: <https://doi.org/10.1088/1755-1315/80/1/012007>
- [23] LI, L. G., HUANG, Z. H., TAN, Y. P., KWAN, A. K. H., & LIU, F. Use of marble dust as paste replacement for recycling waste and improving durability and dimensional stability of mortar. *Construction and Building Materials*, Vol. No. 166, 2018 p.p. 423–432. Available from: <https://doi.org/10.1016/j.conbuildmat.2018.01.154>
- [24] ALI, M., ABDULLAH, M. S., & SAAD, S. A. Effect of Calcium Carbonate Replacement on Workability and Mechanical Strength of Portland Cement Concrete, *Advanced Materials Research*, Vol. No. 1115, 2015 p.p. 137–141. Available from: <https://doi.org/10.4028/www.scientific.net/amr.1115.137>
- [25] TOPCU, I. B., BILIR, T., & UYGUNOGLU, T. Effect of waste marble dust content as filler on properties of self-compacting concrete. *Construction and Building Materials*, Vol. No. 23(5), 2009. Available from: <https://doi.org/10.1016/j.conbuildmat.2008.09.007>
- Indian standards Method of sampling and Analysis of Concrete, IS:1199:1959, Bureau of Indian Standards, New Delhi, India.
- Recommended Guideline for Concrete Mix Design, IS:10262:2019, Bureau of Indian Standards, New Delhi, India.
- Indian Standards Code of Practice – Ordinary Rapid-hardening and Low heat Portland cement, IS:69:1976, Bureau of Indian Standards, New Delhi, India.
- Indian Standards code of practice – Coarse and fine aggregate for concrete, IS:383:2016, Bureau of Indian Standards, New Delhi, India.
- Standard test method for the water absorption of fine aggregates and determining specific gravity of fine aggregates, ASTM C128
- Standard Test Method for Flexural Strength of Concrete (Using Simple Beam with Center-Point Loading), ASTM C293
- Indian Standards code of practice – Method of Test for Strength of Concrete, IS:516:1959, Bureau of Indian Standards, New Delhi, India.
- Compressive Strength of Concrete Method of Test, IS:456:2000, Bureau of Indian Standards, New Delhi, India.
- Splitting Tensile Strength of Concrete Method of Test, IS:5816:1999, Bureau of Indian Standards, New Delhi, India.
- Flexural Strength of Concrete Method of Test, IS:516:1999, Bureau of Indian Standards, New Delhi, India.
- IS Standards code of practice - The object, principle, apparatus, and test procedure of the ultrasonic pulse velocity method, IS:13311:1992, Bureau of Indian Standards, New Delhi, India.
- Non-destructive testing of concrete - Methods of tests, IS:13311 PART 2: 1992, Bureau of Indian Standards, New Delhi, India.
- IS-1124:1974, Method of test for determination of water absorption of concrete – Methods of tests. Bureau of Indian Standards, New Delhi, India.

ABOUT THE AUTHOR



Mohammad Ajmal Khan is a postgraduate research student affiliated to the Department of Civil engineering at Punjabi University, Patiala. He completed his Bachelor of Technology in Civil engineering (2017-21) and Master of Technology in Civil engineering with a specialization in Structural engineering (2021-23) with distinction from Punjabi University, Patiala, India. His research interests are High strength concrete, Sustainable Structural Design, Cement-based Composites, Healthy and green Structures, Carbon capture, Waste Materials Re-use, Industrial by-products, Destructive testing, Non-destructive testing.